

# Overcoming Obstacles in Water Resistant H1 and Biobased Specialty Greases Using Polymer

Erik Willett, PhD  
Vice President, Technology and Development  
Functional Products Inc.

NLGI 2021 Tucson – Paper #2107  
Session 4 – 1:45 PM, Thursday September 30<sup>th</sup> 2021



# Outline

---

- Motivation
- Calcium greasemaking
- Preliminary study in industrial oils
- Three approaches to water resistance in H1 calcium greases in:
  1. Medium solvency H1 petroleum ~40%
  2. Low solvency PAO ~20%
  3. High solvency vegetable oil ~40%
- Summary and Conclusions

# Motivation

---

- Improving water resistance can be *painful*
  - Problem can occur inherently from base oil, thickener, low grade #
  - Far more complex and foundational to fix than adding AO or EP
- Common chokepoints
  1. Updating old greases to new specs without complete reformulation
  2. New greases formulated with limited options like NSF H1 and EAL



# Materials and Methods

---

- NLGI #2 in ISO 150 blends of H1 base stocks
  - Hydrous calcium stearate for petroleum/PAO stocks
  - Calcium stearate-acetate complex (CaX) for veg oil to avoid water
    - St/Ac ratio not a simple 1:1
- ASTM D4049 water sprayoff to measure water resistance
- Observe deficiencies with water resistance and treat with grease polymer


# Calcium and CaX Grease

- Old but enduring technology
- GRAS, HX-1, EAL, MIL
- Robust supply chain
- 13.7% of global grease is Ca
  - Only 4% reported as CaSulf
  - 9.7% still hydrous/anhydrous/complex
    - 280 million pounds

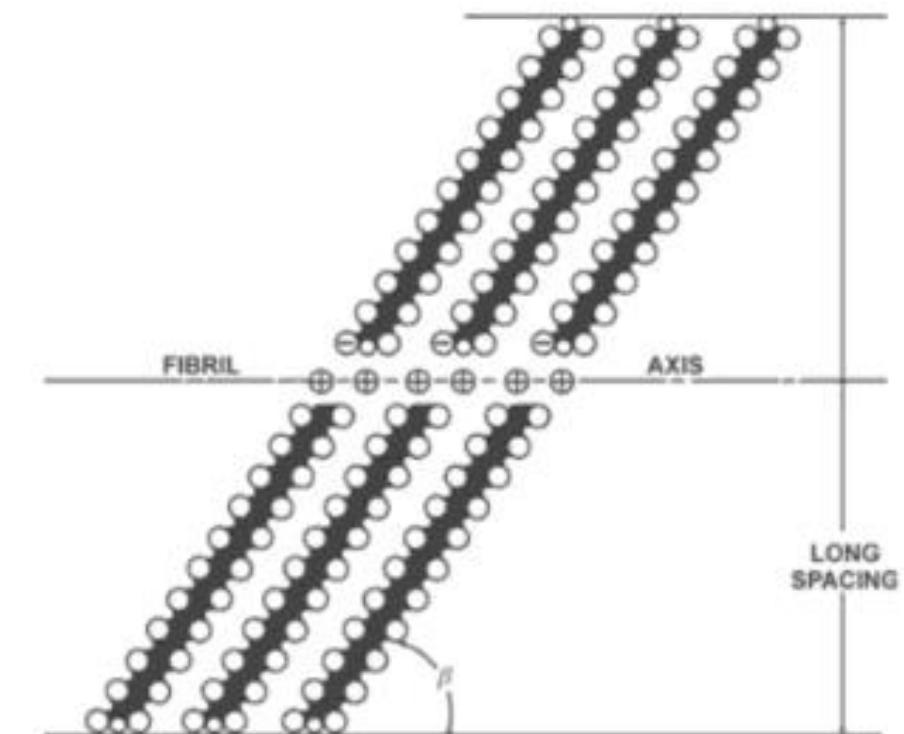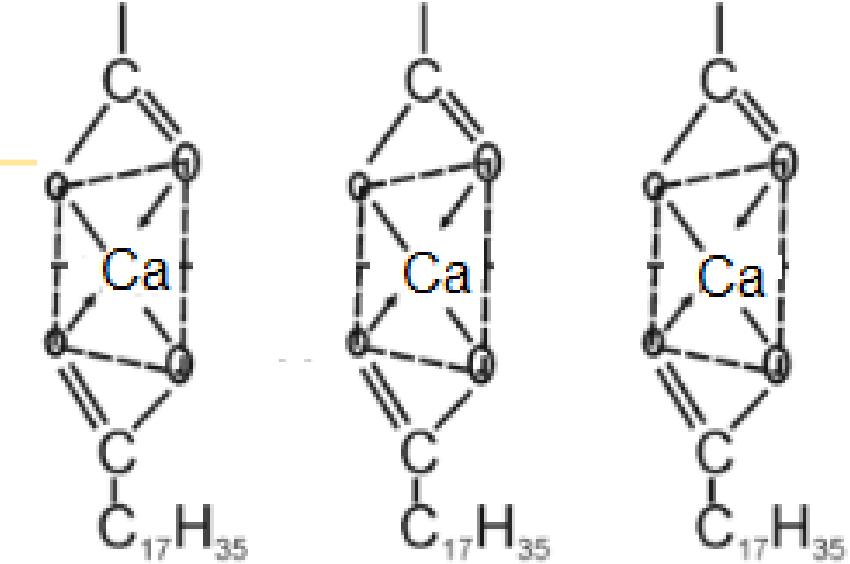


# ASTM D4049 Water Sprayoff

- Static water spray test
  - 38°C/100°F water, 40 psi, 5 minutes
- HPM Water Resistant class
  - <40% WSO target
- Aggressive on soft, polar grease
  - 90%+ WSO in many Ca types
  - Polymer can fix this

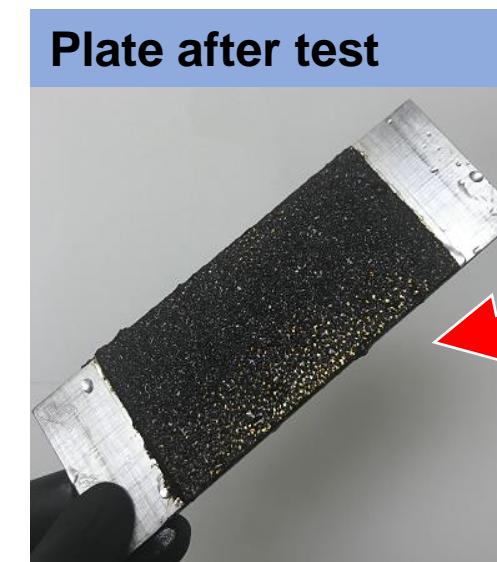


# Grease + Polymer is like Concrete + Rebar

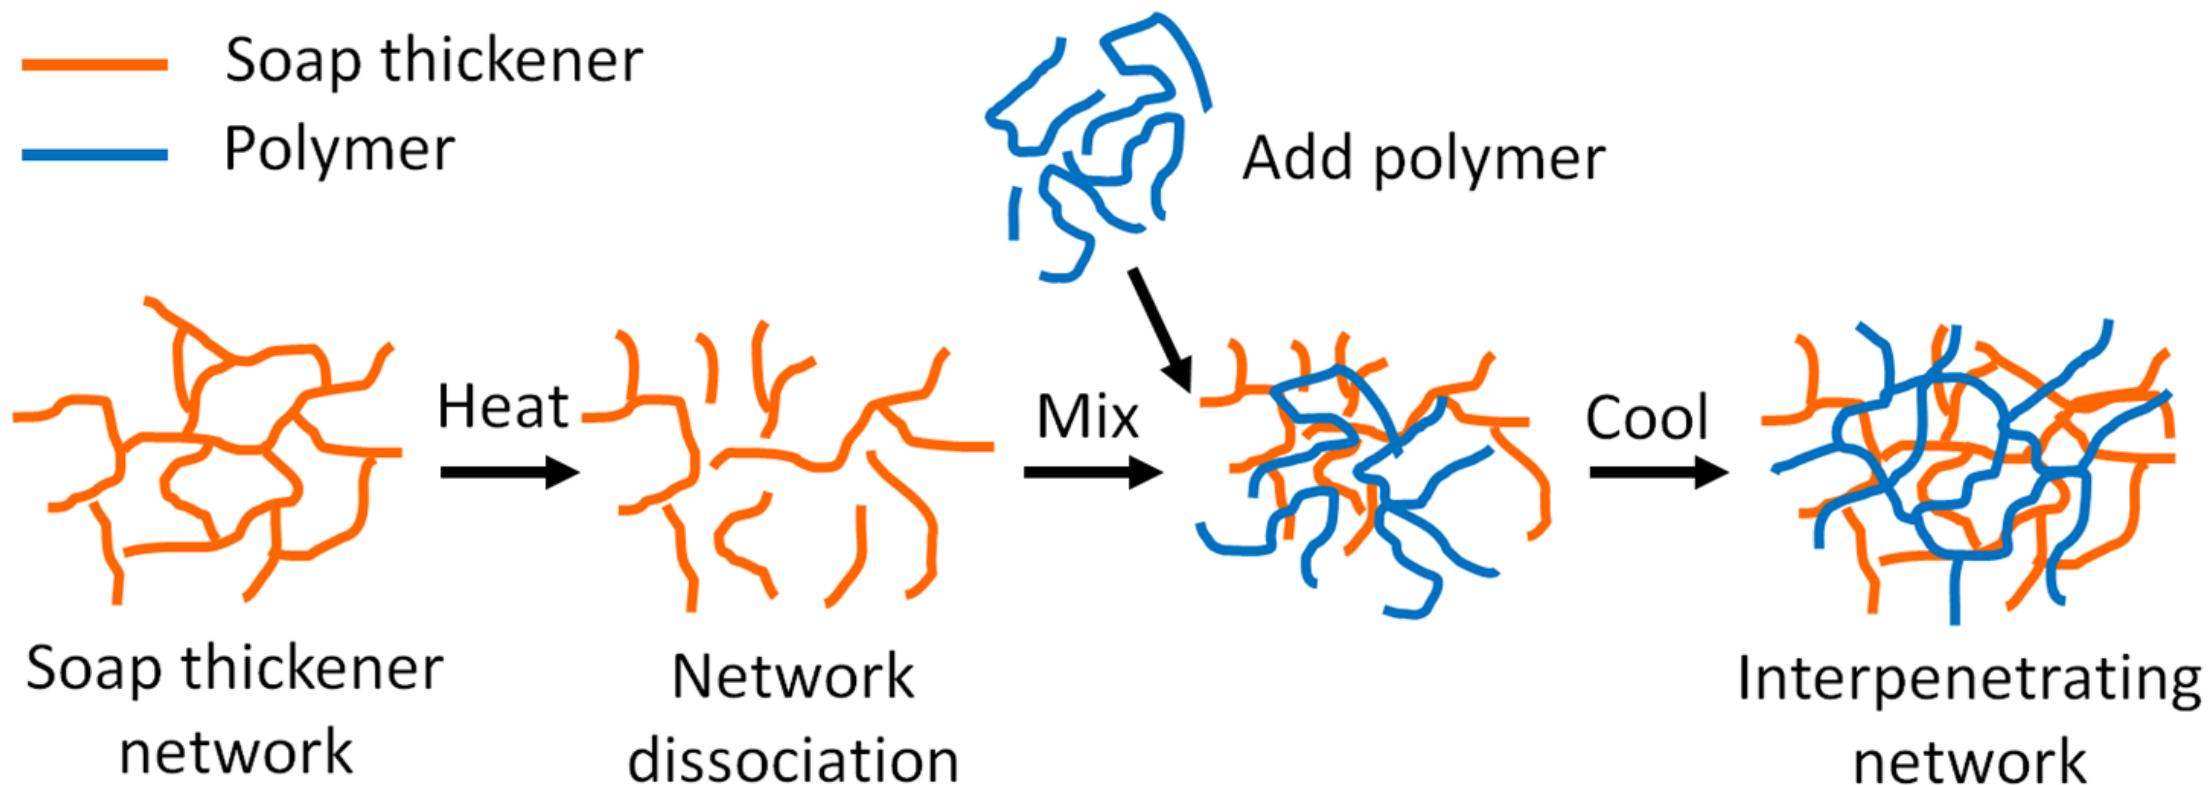

# Starting from a Mystery

- This study begins with an industrial question
- Styrene copolymer grease polymer
  - Excellent WSO *for some*
  - Poor or no effect *for others*
  - Sometimes undesired rubberiness

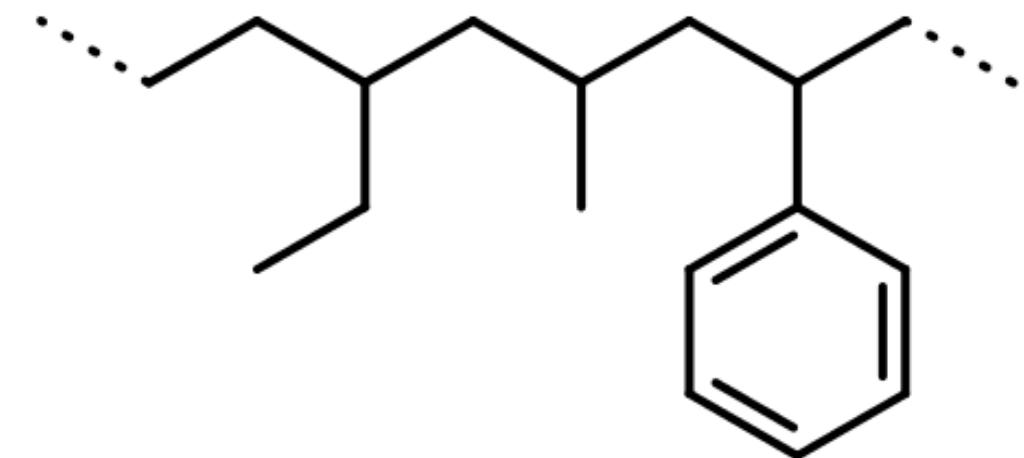


# Early Investigation into Styrene Selectivity

- Hydrous calcium stearate greases with ISO 150 blends of popular oils
  - Paraffinic = 600SN + 150BS
  - Naphthenic = 750 SUS
  - H1 PAO = PAO6 + mPAO100
  - H1 White Oil = 500WO + PIB2500
- Simulating different types of formulators favoring different base oils
- 1wt% styrene grease polymer in each blend + two controls w/o


# Preliminary Results

- Dataset was picked well and we captured the full range of outcomes

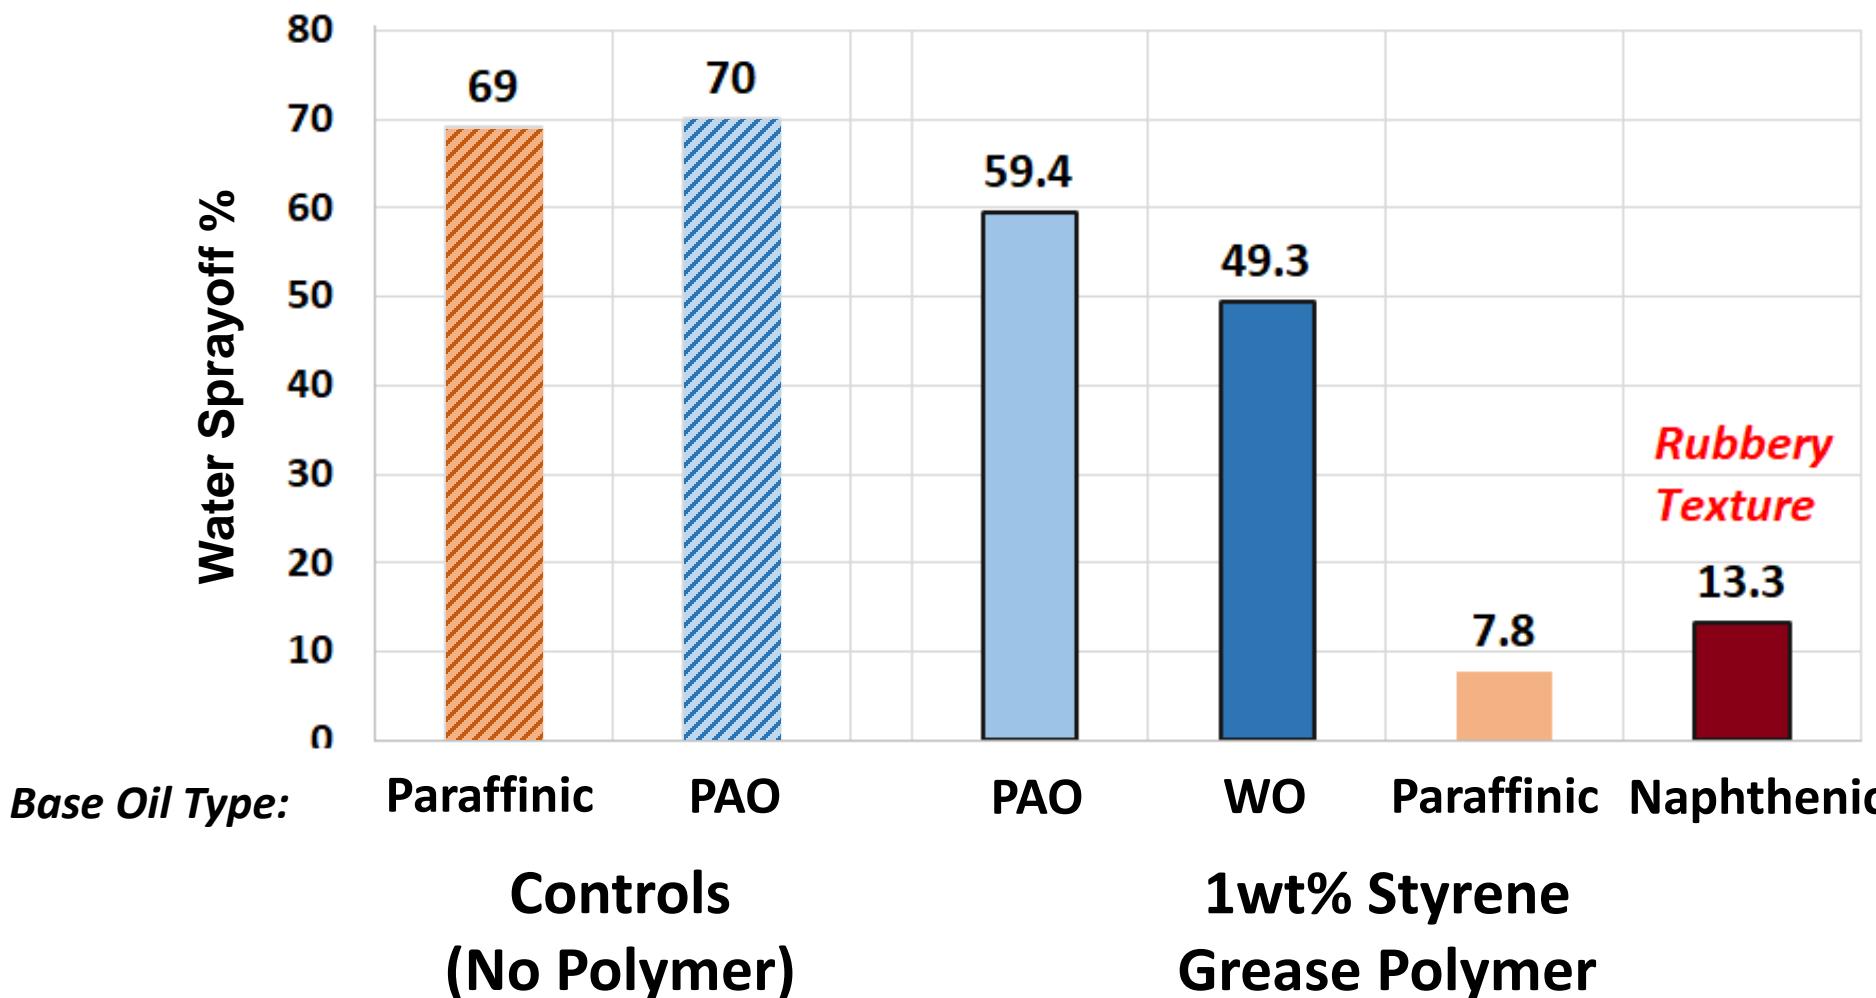

# Styrene Polymer Selectivity

- We can map the range of experiences vs. base oil solvency

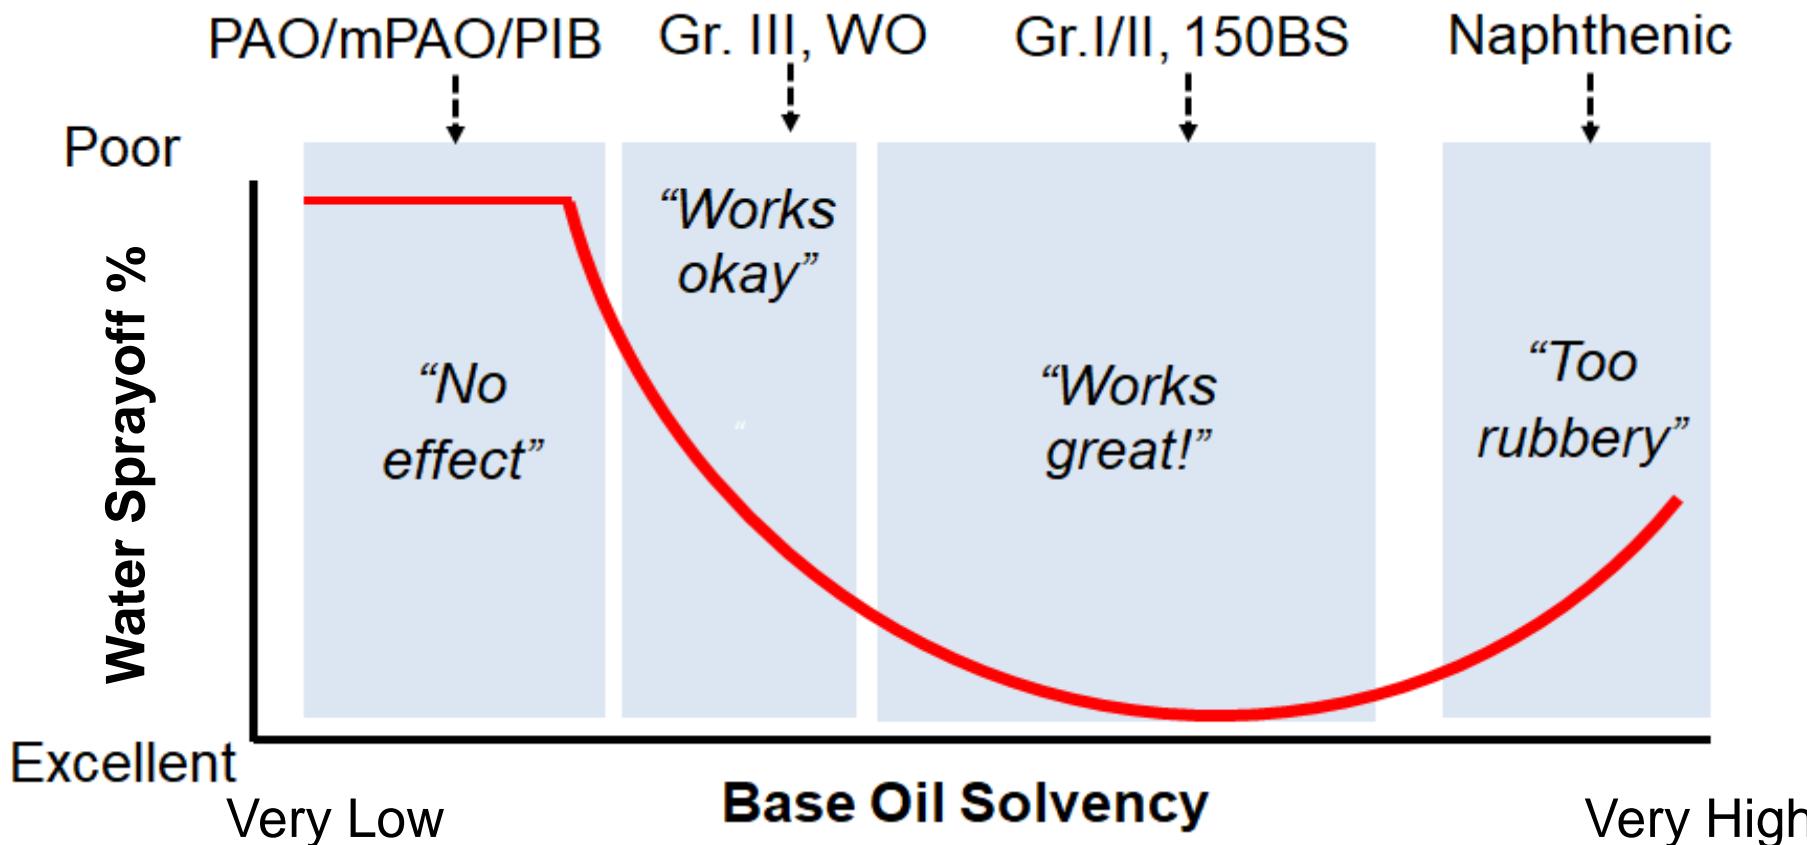

# Qualitative “Solvency”


- Two lessons from comparing oil composition vs. WSO:

1. Naphthenic vs. Paraffinic Oil

- **Aromatic carbon** is key (20% vs. 4%)

2. White Oil vs. PAO


- **Naphthenic carbon** helps to lesser extent (30% vs. 0%)

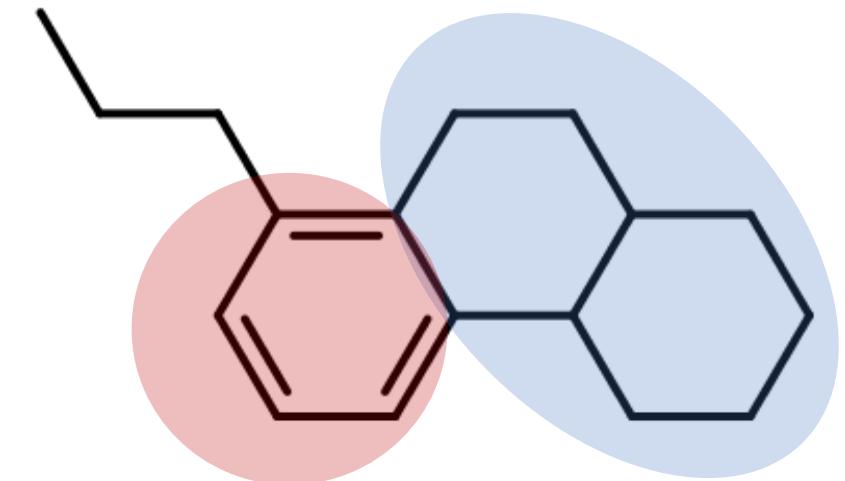


# H1 Base Oils

- Ironically, the styrene polymer is now HX-1 listed
  - But H1 base oils are not known for their high solvency
  - Yet there's more to H1 than just PAO!


White Oil



H1 Group III

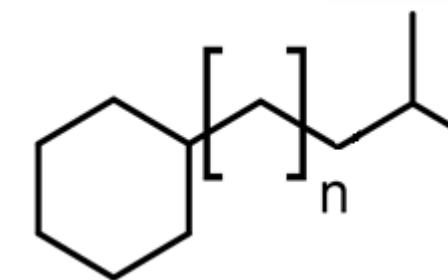


Ethylene-Propylene Oligomer

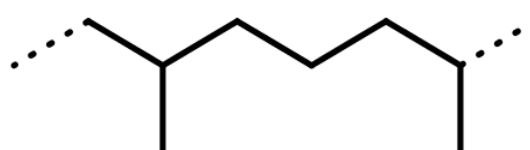

H1 Polybutene



Alkylated  
Naphthalene

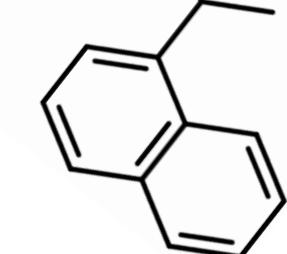

# Designing H1 “Solvency”

---

- Hypothesis: if we reproduce the “solvency” of Group I paraffinic oil using H1 oil blends then we will reproduce the high WSO improvement for H1 grease.
  - To test this we'll need to build from aromatics of alkylated naphthalenes, naphthenes of white oil or Group III, etc.
    - Likely the answer will be very specific so we need a measurable guide
  - We know **% aromatic** and **% naphthenic carbon** are important – start there




# Modeling Solvency vs. WSO%

---

- We're going to capture and quantify "solvency" using two equations we'll feed with data

1. First equation relating important factors of base oil composition to **Solvency**
  - Linear equation adding up different factors multiplied by how important that factor is
    - **Solvency** = a[%aromatic carbon] + b[% naphthenic carbon] + ...
2. Second equation that ties the calculated **Solvency** (x) to our measured **WSO%** (y)
  - Third order polynomial that roughly fits the curvature we saw in the preliminary study
    - **WSO%** = a[**Solvency**]<sup>3</sup> + b[**Solvency**]<sup>2</sup> + c[**Solvency**] + d
    - Use Excel trendline ("regression") to fit Solvency to WSO%
    - The R<sup>2</sup> of this regression is our compass to guide our equation optimizing

# Iterative Workflow

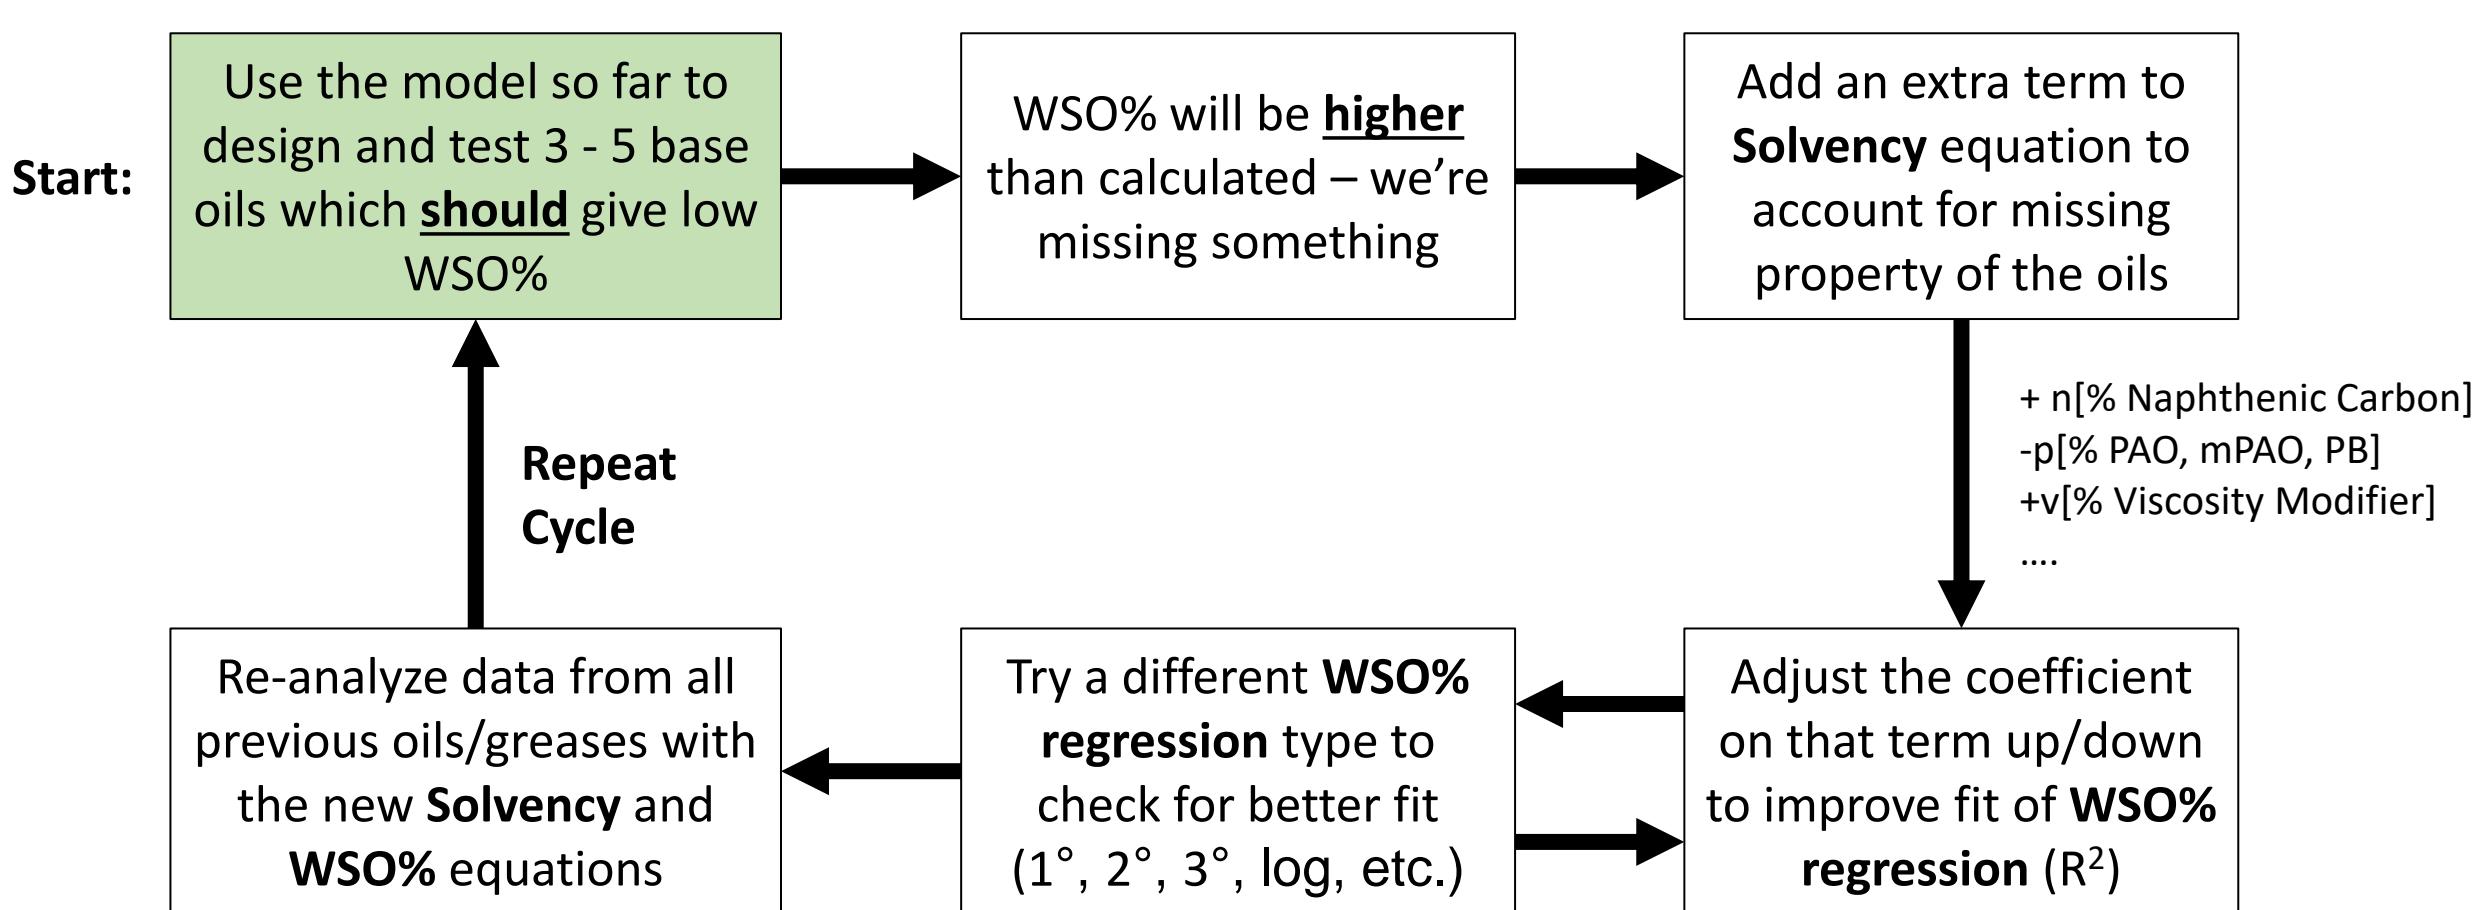


# After Many Iterations...

**Solvency** = 1.00 x (% Aromatic Carbon)  
+ 0.24 x (% Naphthenic Carbon)  
- 0.07 x (% PAO + mPAO + PIB)  
+ 0.10 x (% VM in light white oil)


## WSO% vs. Solvency:

- best fit by 3<sup>rd</sup> order polynomial in Excel
- (really more of a 'square-root' sign)

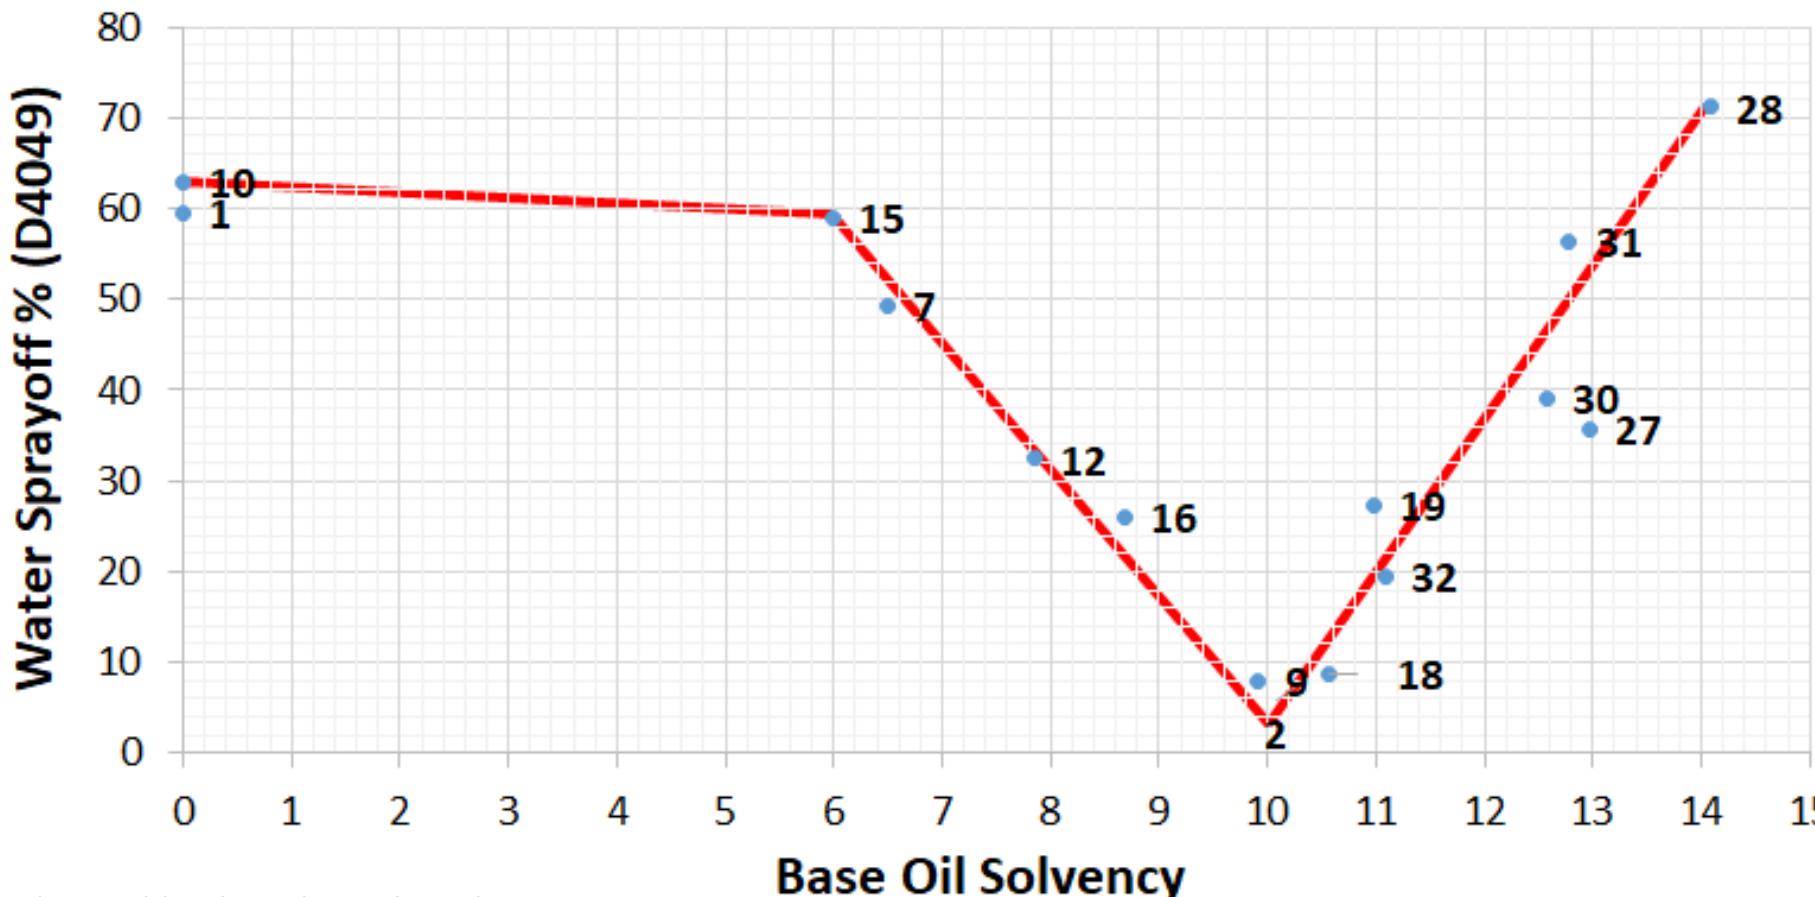


# Low Solvency Case

- What if we want to or have to use full PAO/mPAO?
  - No naphthenes or aromatics for solvency

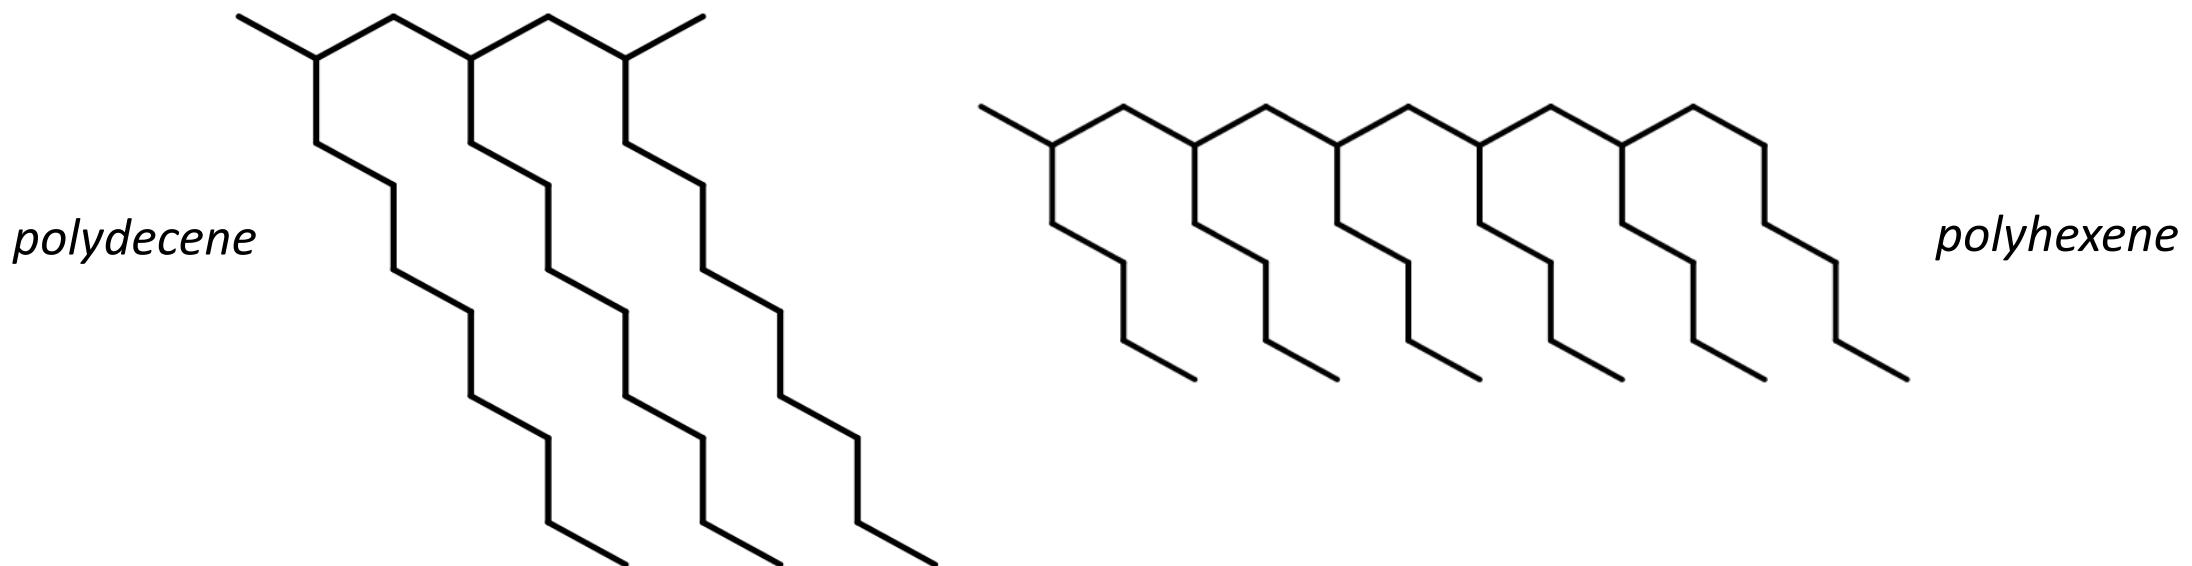


# Tuning the Polymer for PAO

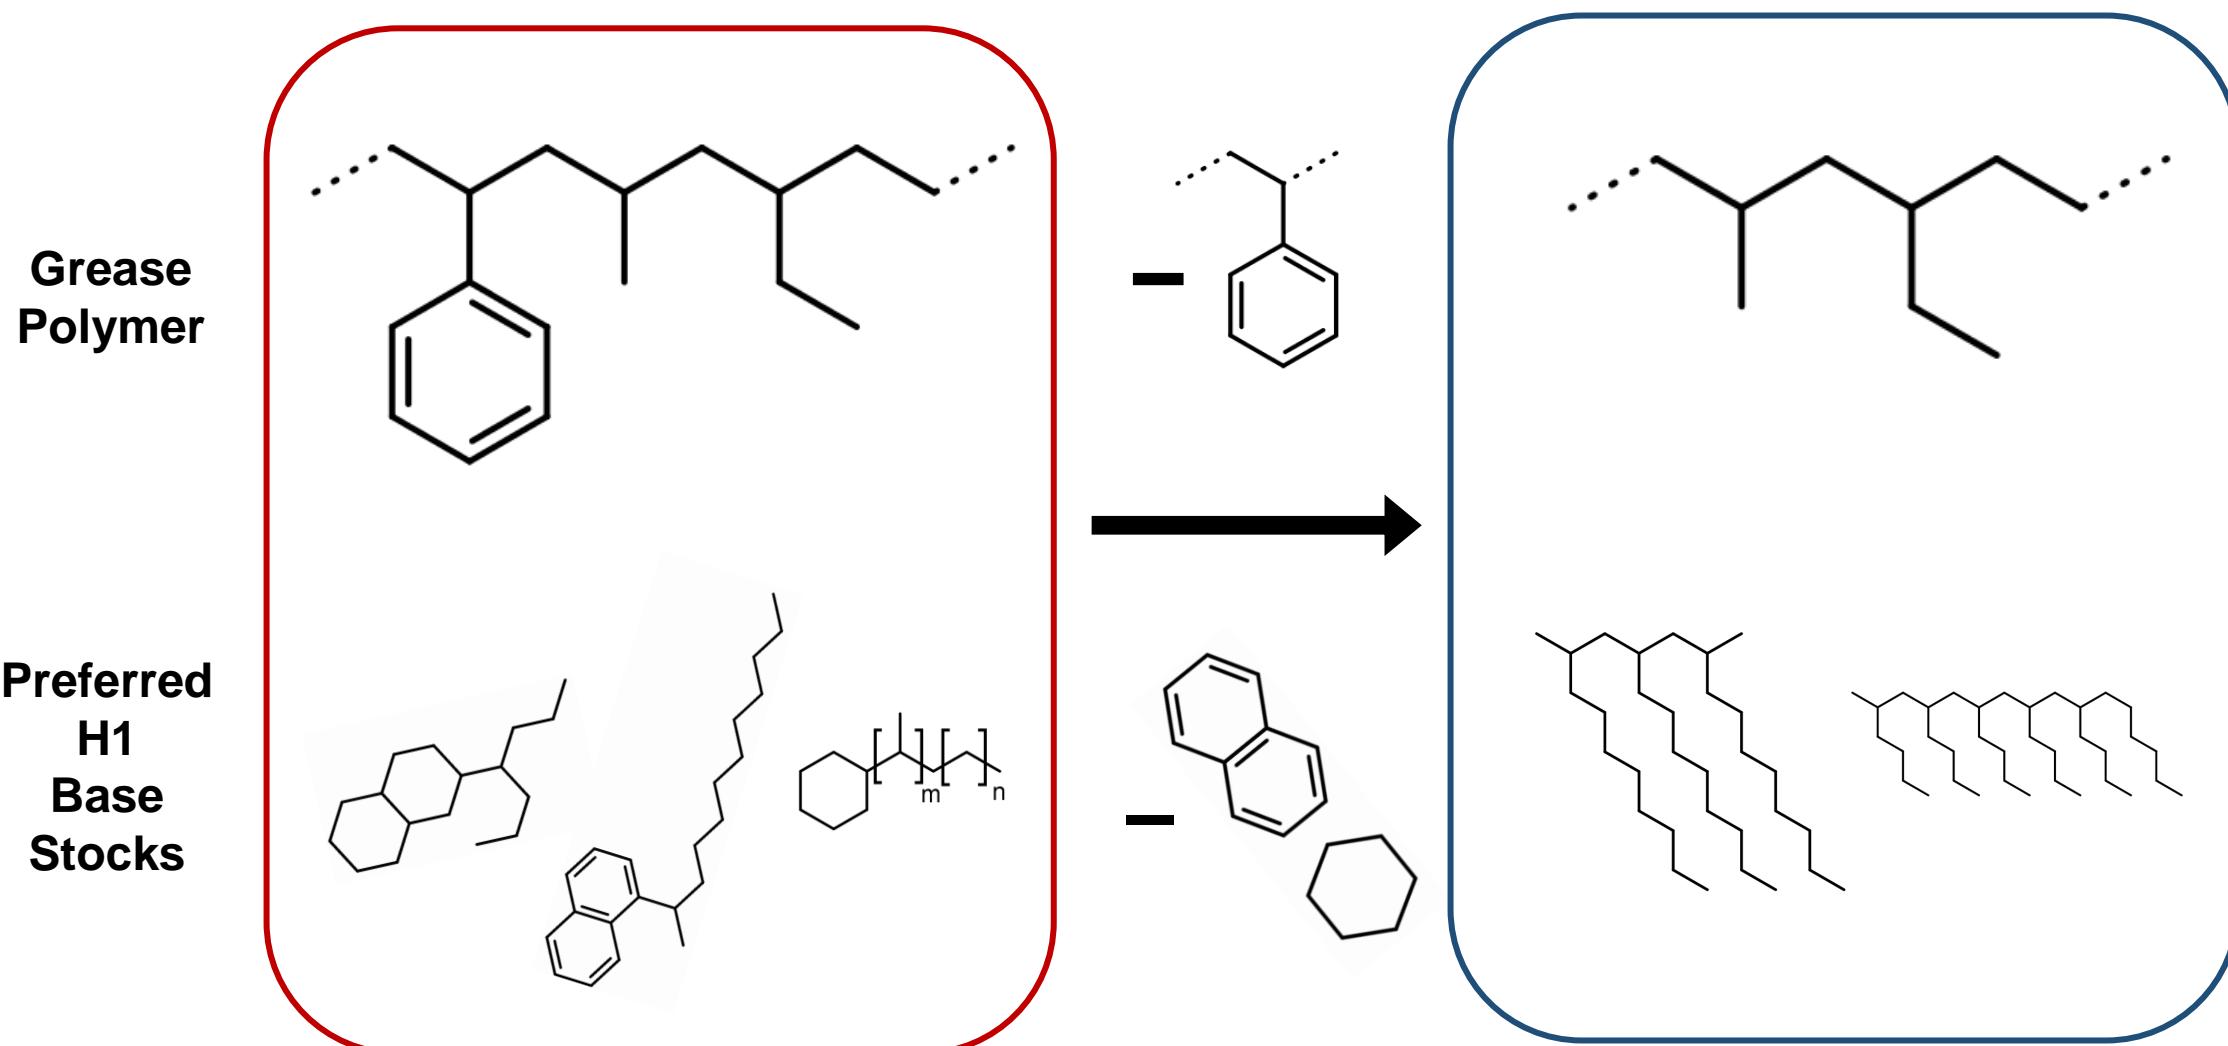

# HX-1 Polyolefin

- HX-1 polyolefin isn't effective at 1wt% vs. HX-1 styrene polymer
- Yet at lower cost, we can uptreat - sometimes the solution is that simple

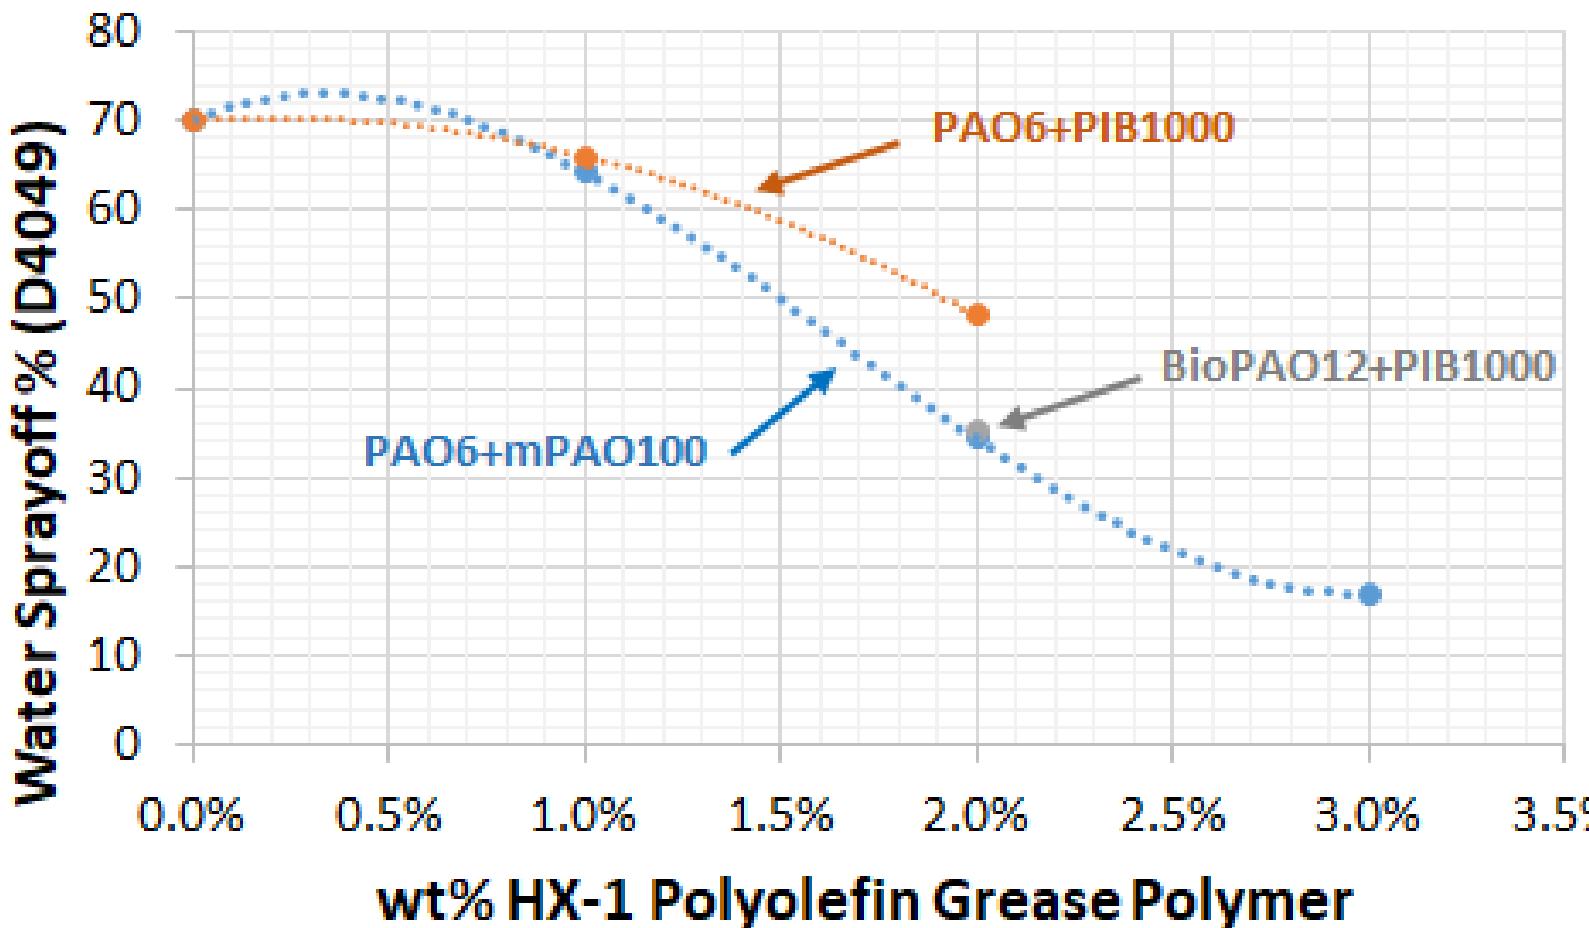

**1.75wt% for 40% WSO**

**2.50wt% for 20% WSO**

# Environmentally Acceptable Grease

- Vegetable oils are an ideal EAL base stock in principle
  - 100% biobased/renewable/biodegradable
  - Typically  $\leq$  33% the price of synthetics
- First problem is viscosity
  - Limited to ISO ~32, no other “cuts”
  - Other problems too but viscosity is most glaring



# Biobased Grease Approach

---


- We'll tackle vegetable based grease as a matter of low base oil viscosity
  - Three biobased viscosity modifiers on hand (one is HX-1)
    - We'll use each to build ISO 150 calcium complex greases
      - Does VM selection matter at same ISO VG and grade?
      - Which biobased VM chemistry works best?
      - Any other benefits?




# Biobased VMs

- Esters are highly discerning – ideally the VM ‘looks’ like the base fluid
  - Polarity, branching, MW, saturation determine fit


*triglyceride*

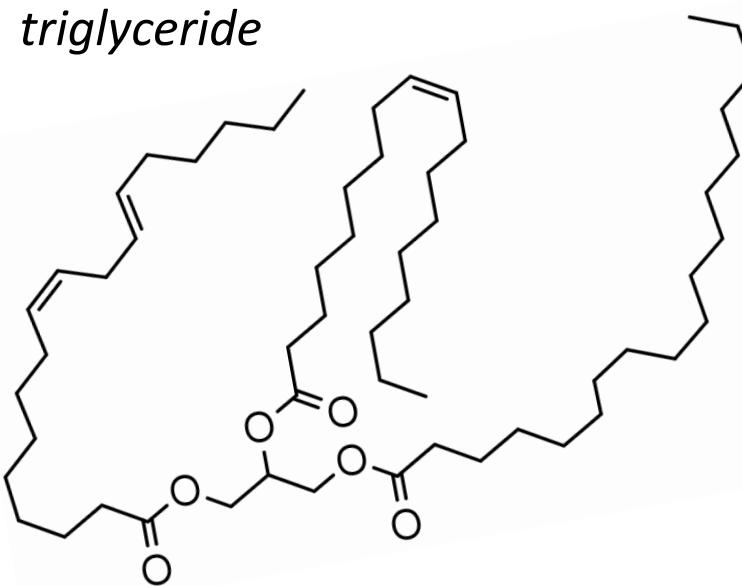

Alkene




Styrene




Ether



Ester



Amide



Polarity of Functional Group


# Greasemaking with Liquid Bio VM's

- Three different biobased viscosity modifier chemistries tested
- Same ISO VG and grade, different yields and WSO

| Grease Formulations by wt%      | No VM Control | High MW Bio VM | Low Temp Bio VM | HX-1 Bio VM |
|---------------------------------|---------------|----------------|-----------------|-------------|
| Calcium Stearate/Acetate Powder | 40.0          | 30.0           | 28.5            | 22.5        |
| Antioxidant Blend               | 2.0           | 2.0            | 2.0             | 2.0         |
| <i>Biobased VM (various)</i>    | --            | 11.6           | 12.7            | 12.8        |
| High Oleic Canola Oil           | 58.0          | 56.4           | 56.8            | 62.7        |
| <b>NLGI Grade</b>               | #2            | #2             | #2              | #2          |
| <b>Base Oil Blend ISO VG</b>    | 32            | 150            | 150             | 150         |
| <b>Water Sprayoff % (D4049)</b> | 99.0%         | 95.5%          | 74.8%           | 31.2%       |

# Bio VM Analysis


- What's driving the large difference in WSO?
- Amount of polymer delivered (solids content) appears most important

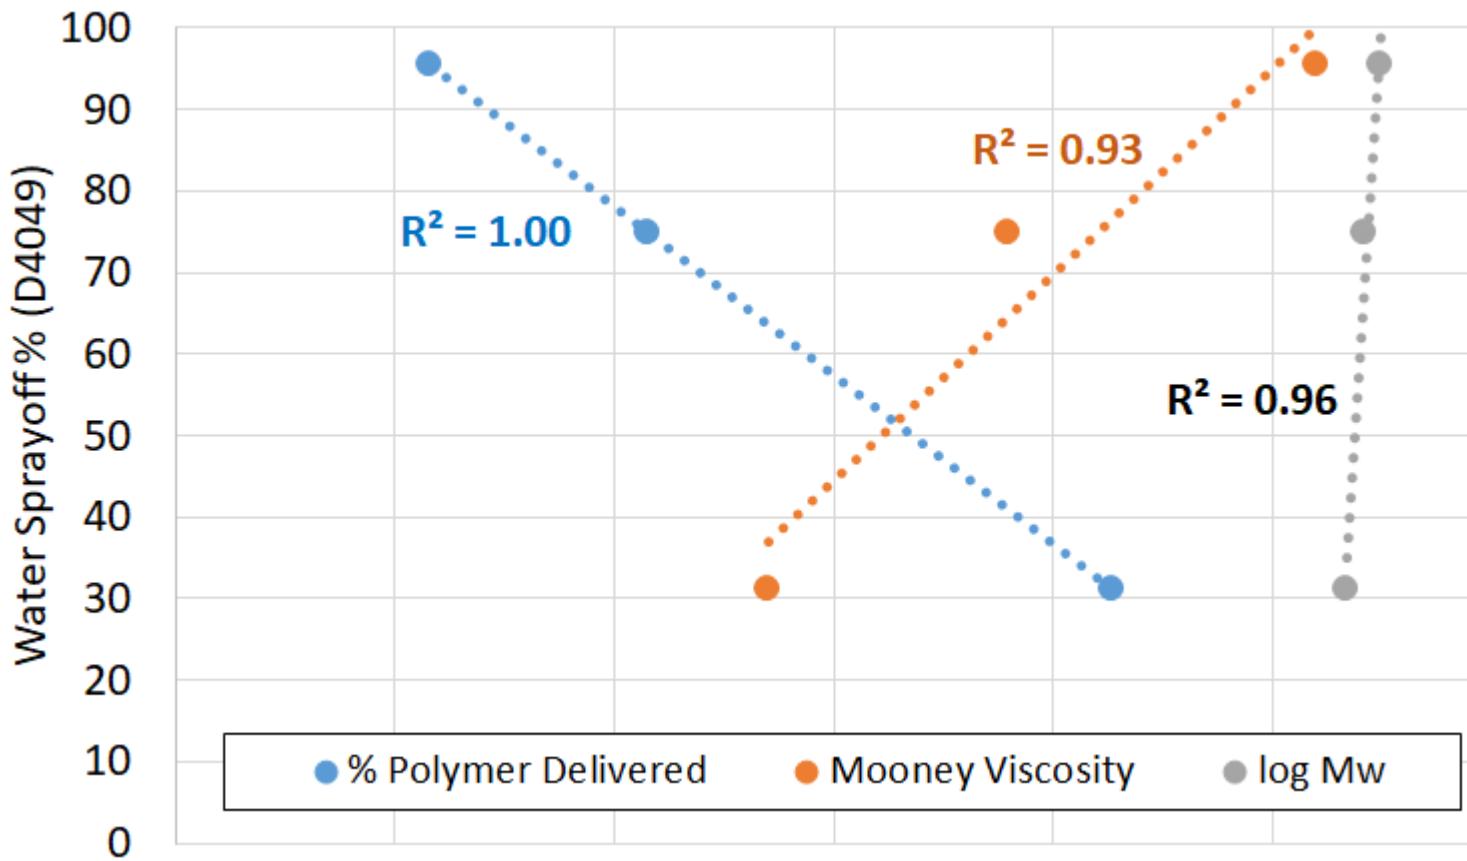

# Putting It All Together (1/3)

H1  
Grease  
Base  
Stock...


H1  
Group III  
White Oil  
Alkyl. Naph.

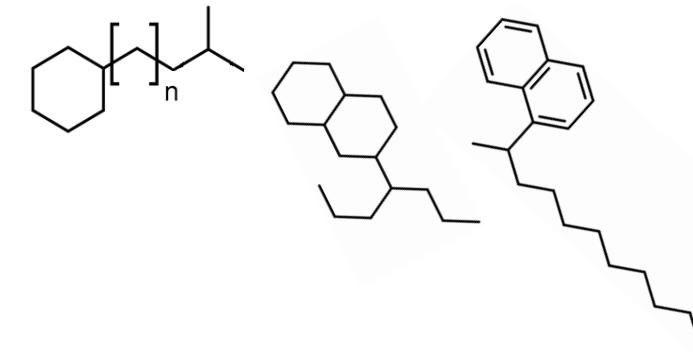

**Solvency**

... and  
Preferred  
Polymer


**HX-1 Styrene  
Grease Polymer  
(1wt%)**

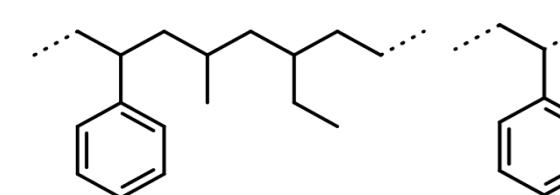


# Putting It All Together (2/3)

H1  
Grease  
Base  
Stock...

mPAO  
PAO  
EPO  
PIB

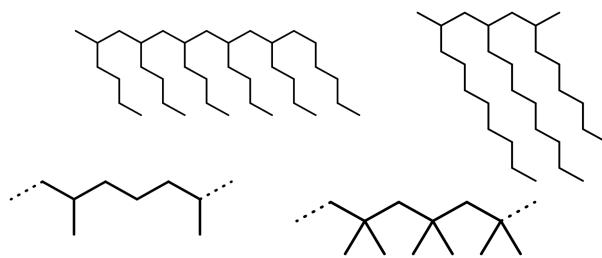


H1  
Group III  
White  
Oil  
Alkyl.  
Naph.

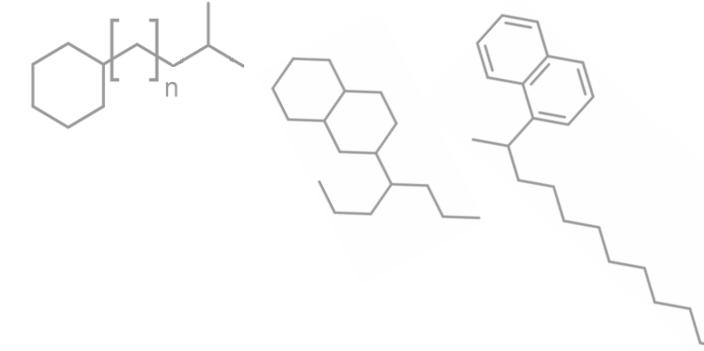


**Solvency**

**HX-1 Polyolefin  
Grease Polymer  
(2-3wt%)**


... and  
Preferred  
Polymer

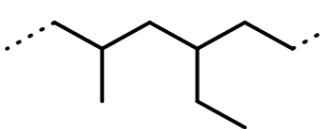

**HX-1 Styrene  
Grease Polymer  
(1wt%)**

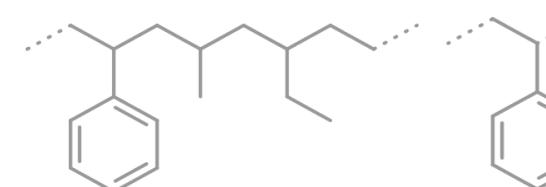

# Putting It All Together (3/3)

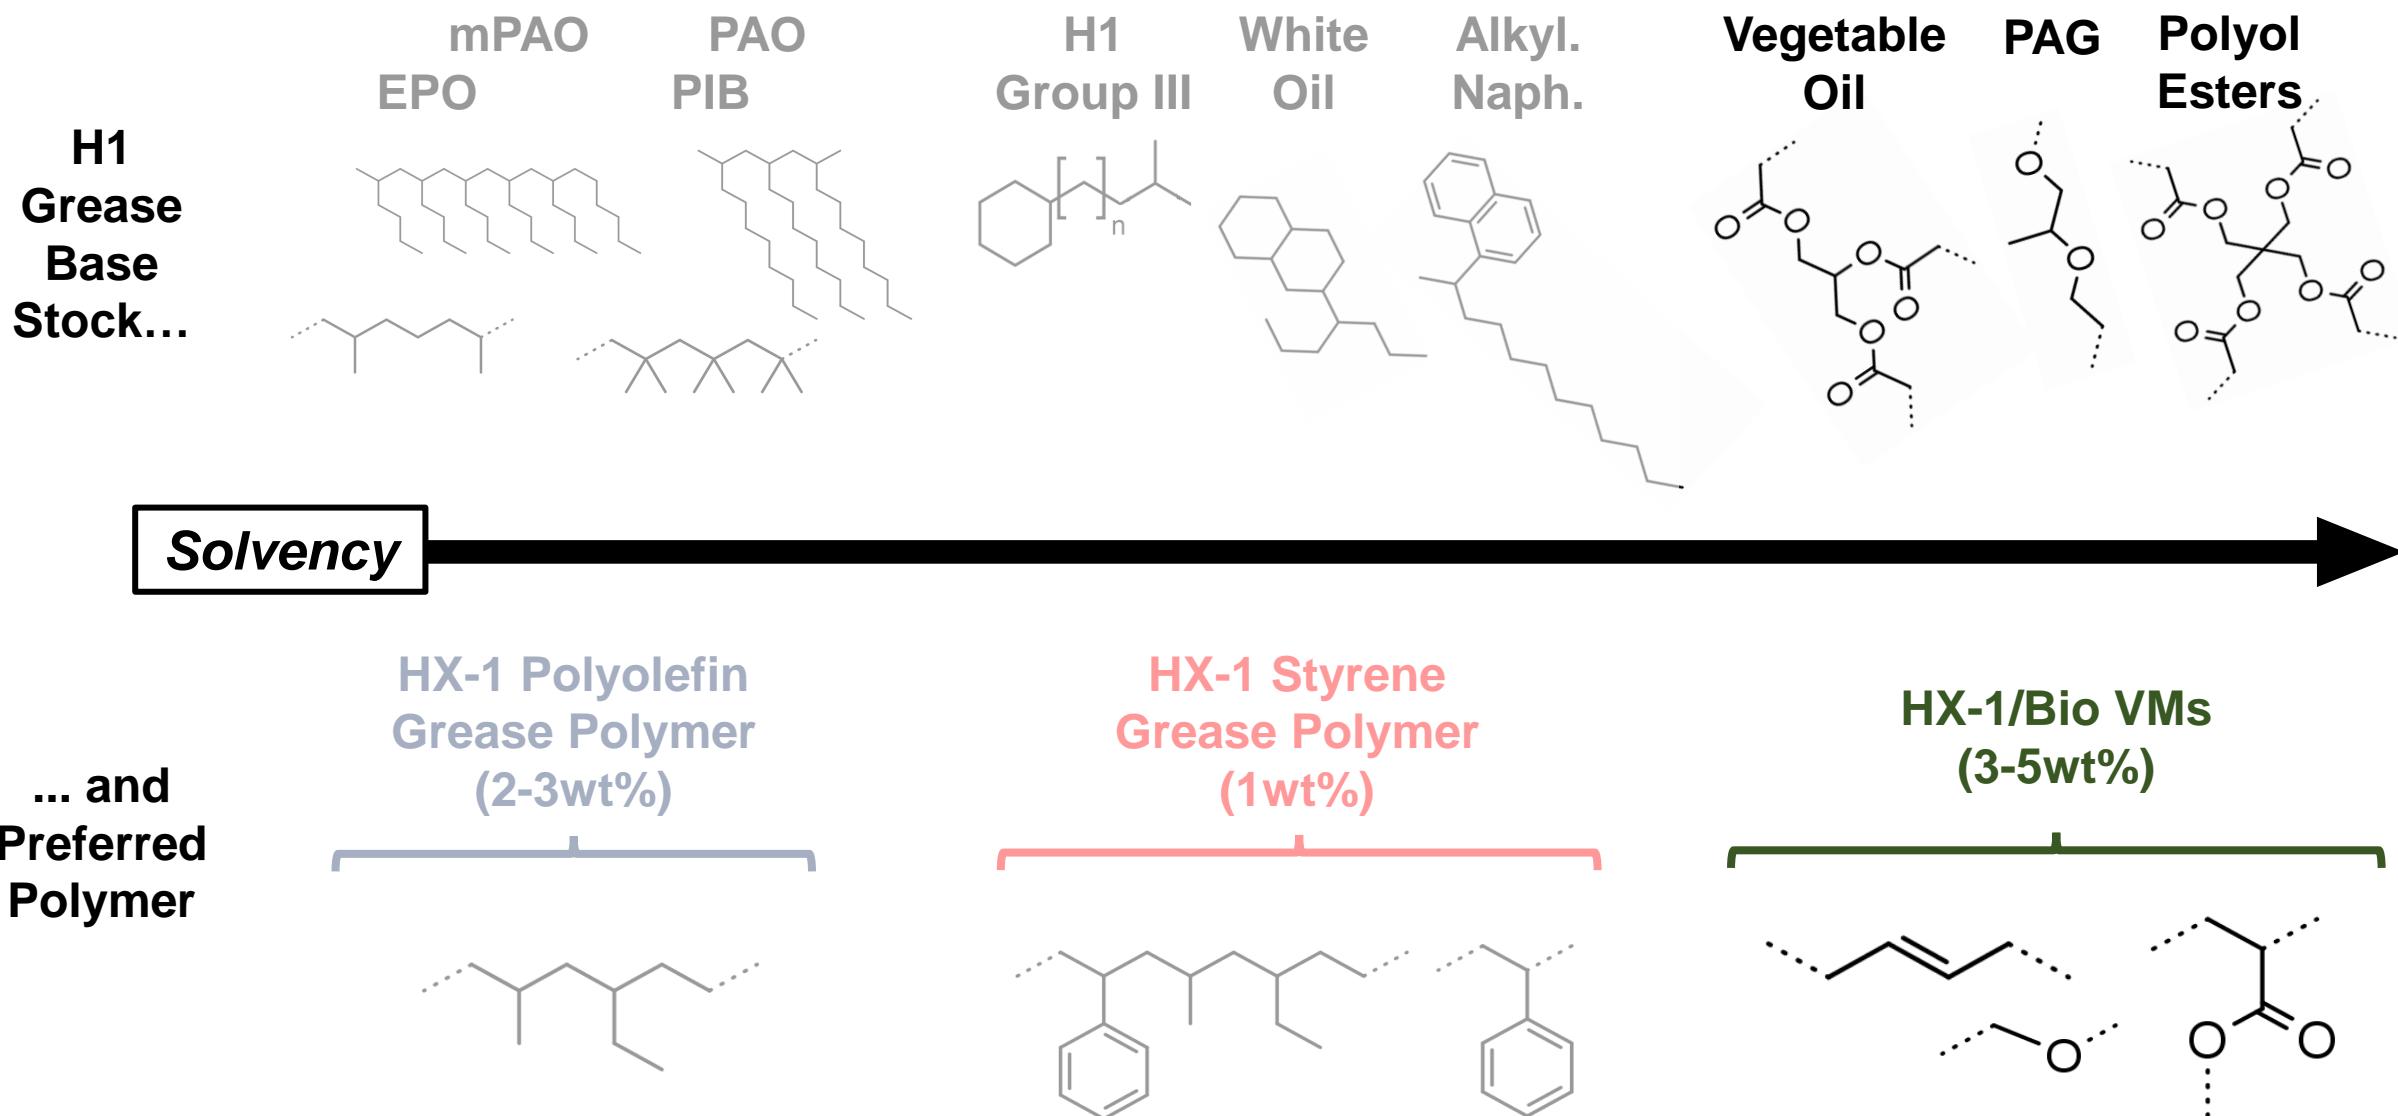

# Conclusions

---

- Worked the problem to define the parameters of an oil-selective high performance polymer
  - Able to translate from industrial to H1 stocks
- Developed math to engineer H1 blends with petroleum solvency
- Produced recommendations for H1 grease polymer selection based on base oil stock – low/medium/high solvency



# Future Work

---

- Extend biobased water resistance to <20% WSO – stuck at 31%
- Water washout (ASTM D1264) is still key to GC-LB and HPM
- Other H1 or EAL thickeners? CaSulf, AlX, Silica?

# Thank you!

[ewillett@functionalproducts.com](mailto:ewillett@functionalproducts.com)  
[www.functionalproducts.com](http://www.functionalproducts.com)

